


13Kh11N2V2MFL

13KH11N2V2MF

6

1

10	1 6
----	-----

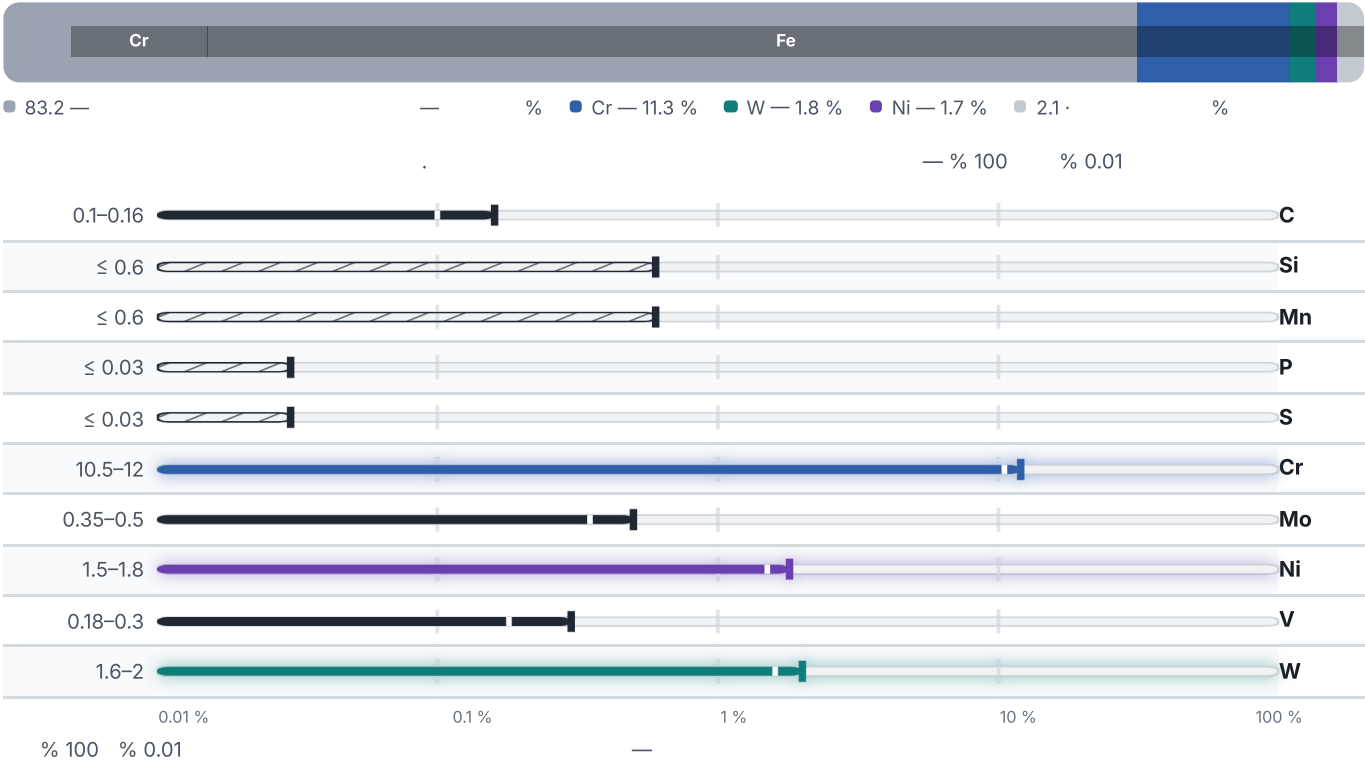

()

3	11				
KCU kJ/m ²	Z %	A5 %	RE N/mm ²	RM N/mm ²	.
880	55	15-13	930-735	1080-880	Bar, GOST 5949-75
KCU kJ/m ²	Z %	A5 %	RE N/mm ²	RM N/mm ²	.
600	50	10	850	950	Blank
HB					.
269					13KH11N2V2MF (13X11H2B2MΦ) , Bar GOST 5949-75

0					
LAMBDA W/(m·K)	ALPHA K/6-^10	E GPa	RHO g/cm ³	.	
20.9	—	200	7.8		20
22.3	11	198	—		100
24	11.7	187	—		200
25	12.2	175	—		300
27.2	13.3	165	—		400
—	—	157	—		450
28	13	145	—		500
—	—	125	—		550
28.5	13.3	109	—		600
28.9	—	—	—		700
31.4	—	—	—		800

1	6				
		6		/	
		gost	13KH11N2V2MF		
		gost		13Kh11N2V2MFL	
		gost		13X11H2B2MΦ	
		gost		1X12H2BMΦ	
		gost		ЭИ961	
		gost		ЭИ961Л	

EN 10204 2.1	.EN 10204	.	.	3.2	3.1
--------------	-----------	---	---	-----	-----

13Kh11N2V2MFL

--

2026/08/18

—