

MATERIAL NUMBER 1.4372 · CLASS 1.4

20201

Material no. 1.4372

also listed as X12CrMnNiN17-7-5


Chemical composition, mechanical and physical property values, and 27 standard designations from 9 regions.

DENSITY	ELASTIC MODULUS	OTHER DESIGNATIONS	PROPERTY VALUES
7.85 g/cm ³	197 GPa	27 in 9 regions	14 on file


Chemical composition

Mass fraction in %

What this alloy is

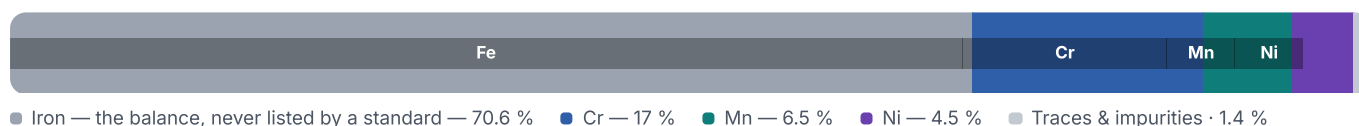

Logarithmic scale, 0.01 % to 100 % — every value here compares directly, decade by decade.

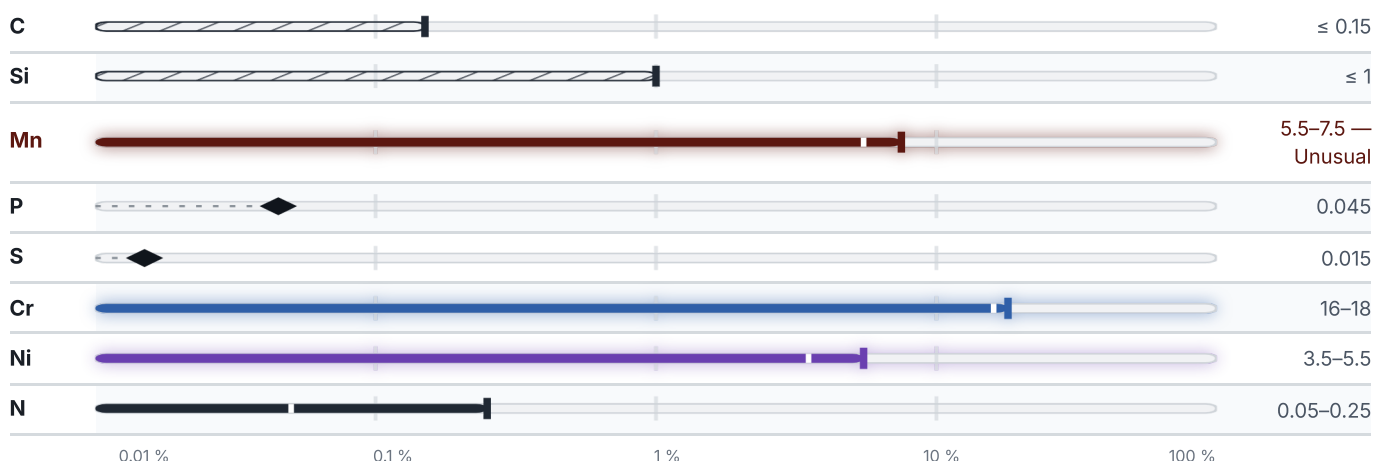

The scale is logarithmic, not the element's raw share of the alloy — the only honest way to fit 0.01 % and 100 % in one picture, and it means every value here can be compared with every other.

Predicted transformation temperatures

Not enough recorded composition to predict a transformation temperature for this grade — missing: Mo.

Mechanical properties

5 values across 2 conditions

CONDITION · DIMENSION	RM N/mm ²	RE N/mm ²	A %	Z %
Bars/Rods	520	275	40	45
SOFT ANNEALED				HB
Soft annealed				260

Physical properties

6 values

PROPERTY	VALUE	UNIT
Density	7.85	g/cm ³
Elastic modulus	197	GPa
Thermal expansion coefficient	15.7	10 ⁻⁶ /K
Thermal conductivity	15	W/(m·K)
Specific heat capacity	500	J/(kg·K)
Electrical resistivity	700	nΩ·m

Heat treatment

1 regimes

STEP	TEMPERATURE	MEDIUM
Solution annealing	Temperature not stated	—

Designations across standards

27 designations · 3 documented as identical

United States		14	China		3
S20100	This grade's own name	uns	12Cr17Mn6Ni5N		gb
S20200		uns	12Cr18Mn9Ni5N		gb
201	This grade's own name	aisi-sae	1Cr17Mn6Ni5N		gb
202		aisi-sae			
20201		aisi-sae	Russia / CIS		3
S20100		aisi-sae	12Ch17G9AN4		gost
A1012		astm	12X17Г9AH4		gost
A213		astm	EI878		gost
A240		astm			
A249		astm	Japan		2
A276		astm	SUS201		jis
A473		astm	SUS202		jis
A480		astm			
A666		astm	Europe		1
			X12CrMnNiN17-7-5	This grade's own name	din-en

France	1	Poland	1
Z12CMN17-07Az	afnor	1H17N4G9	pn
International	1	South Korea	1
X12CrMnNiN18-9-5	iso	STS201	ks

Note on use. The data is compiled to the best of our knowledge from publicly available standards and manufacturer documentation. It replaces neither material testing nor an inspection document to EN 10204. Please request a mill certificate to EN 10204 2.1, 3.1 or 3.2 together with your enquiry. The standard in its current valid edition always prevails.

Enquiry about 20201

Quotation, availability, mill certificate or a technical question — directly on the material page.

[Start an enquiry](#)

DATASHEET ONLINE

View the material page

GRADE SEARCH

Search all grades

MATERIAL NO.

1.4372

ISSUED

Aug 20, 2026