

MATERIAL NUMBER 1.8836 · CLASS 1.8

S420ML

Material no. 1.8836


Chemical composition, mechanical and physical property values, and 6 standard designations from 3 regions.

DENSITY 7.85 g/cm ³	OTHER DESIGNATIONS 6 in 3 regions	PROPERTY VALUES 15 on file
--	---	--------------------------------------


Chemical composition

Mass fraction in %

What this alloy is

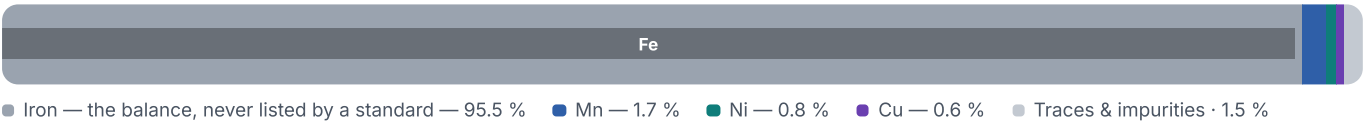

Logarithmic scale, 0.01 % to 100 % — every value here compares directly, decade by decade.

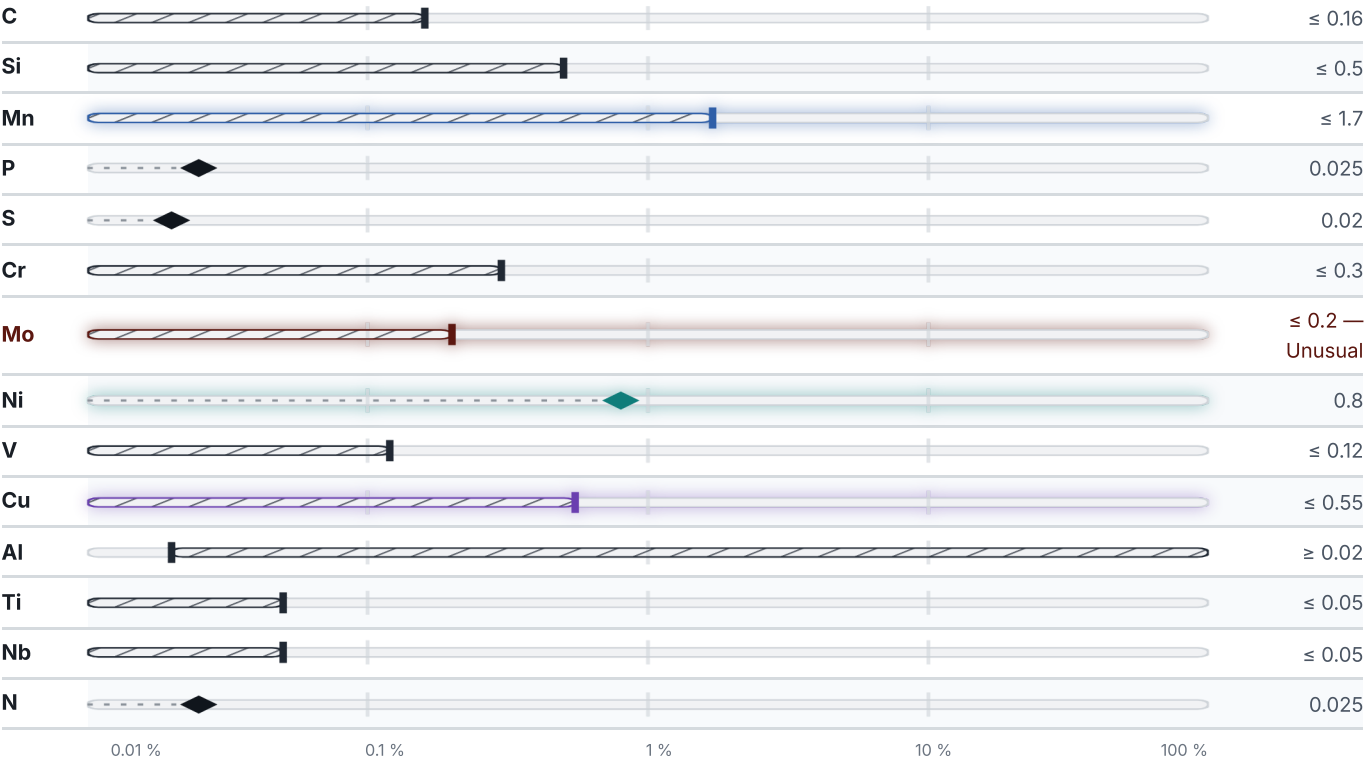

The scale is logarithmic, not the element's raw share of the alloy — the only honest way to fit 0.01 % and 100 % in one picture, and it means every value here can be compared with every other.

Predicted transformation temperatures

computed from composition · °C

PREDICTED AE3 810 °C	PREDICTED AE1 706 °C	PREDICTED ACM 403 °C	PREDICTED BS 538 °C
-------------------------	-------------------------	-------------------------	------------------------

Mechanical properties

11 values across 1 conditions

CONDITION · DIMENSION	REH N/mm²	RM N/mm²
≤ 16	420	–
16 – 40	400	–
≤ 40	–	520–680
40 – 63	390	500–660
63 – 80	380	480–640
80 – 100	370	470–630
100 – 120	365	460–620

Physical properties

1 values

PROPERTY	VALUE	UNIT
Density	7.85	g/cm³

Designations across standards

6 designations · 1 documented as identical

Europe	3	United States	2
FeE420KTTM	din-en	K12202	uns
S420ML This grade's own name	din-en	A633Gr.E	aisi-sae
TStE 420 TM	din-en		
		France	1
		E420FP	afnor

Note on use. The data is compiled to the best of our knowledge from publicly available standards and manufacturer documentation. It replaces neither material testing nor an inspection document to EN 10204. Please request a mill certificate to EN 10204 2.1, 3.1 or 3.2 together with your enquiry. The standard in its current valid edition always prevails.

Enquiry about S420ML

Quotation, availability, mill certificate or a technical question — directly on the material page.

Start an enquiry

DATASHEET ONLINE	GRADE SEARCH	MATERIAL NO.	ISSUED
View the material page	Search all grades	1.8836	Aug 20, 2026