

MATERIAL NUMBER 1.7016 · CLASS 1.7

15G2AFDps

Material no. 1.7016

also listed as 17Cr3


Chemical composition, mechanical and physical property values, and 36 standard designations from 11 regions.

DENSITY 7.85 g/cm ³	OTHER DESIGNATIONS 36 in 11 regions	PROPERTY VALUES 10 on file
--	---	--------------------------------------


Chemical composition

Mass fraction in %

What this alloy is

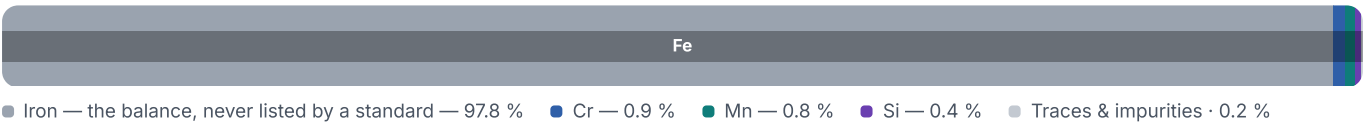

Logarithmic scale, 0.01 % to 100 % — every value here compares directly, decade by decade.

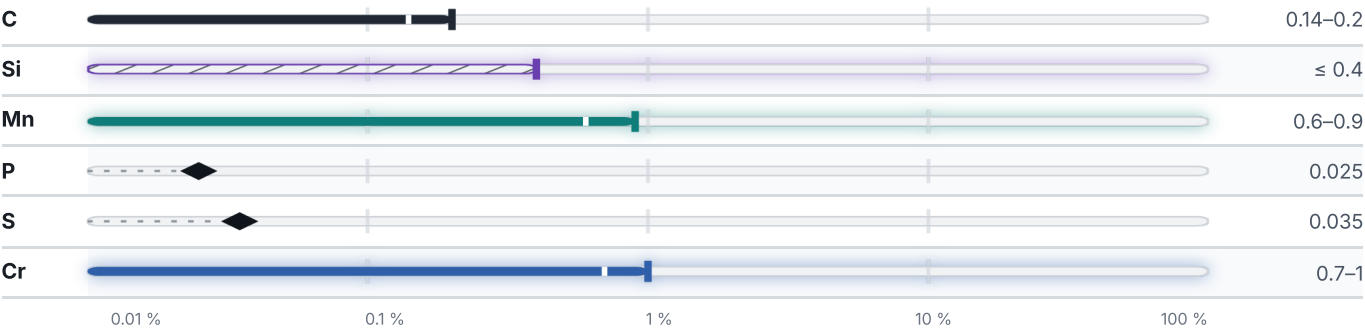

The scale is logarithmic, not the element’s raw share of the alloy — the only honest way to fit 0.01 % and 100 % in one picture, and it means every value here can be compared with every other.

Predicted transformation temperatures

Not enough recorded composition to predict a transformation temperature for this grade — missing: Ni, Mo.

Mechanical properties

13 values across 5 conditions

SOFT ANNEALED	HB	HRB	HV
Soft annealed	174	84	170
CONDITION · DIMENSION	RM N/mm ²	RE N/mm ²	A5 %
5 - 9	560	400	18
TREATED TO FERRITE-PEARLITE STRUCTURE AND HARDNESS RANGE			HB
Treated to ferrite-pearlite structure and hardness range			140–187
CONDITION · DIMENSION	RM N/mm ²	RE N/mm ²	A5 %
to 50	510	390	19
CONDITION · DIMENSION	RM N/mm ²	RE N/mm ²	A5 %
to 50	530	390	18

Physical properties

4 values

PROPERTY	VALUE	UNIT
Density	7.85	g/cm ³
Transformation point Ac1	720	°C
Transformation point Ac3	850	°C

Technological properties

PROPERTY	VALUE	UNIT
Weldability	without limitations.	

Designations across standards

36 designations · 12 documented as identical

Russia / CIS		14	United Kingdom		2
15Ch	gost		17CrS3	bs	
15G2SF	gost		527M17	bs	
15G2SFD	gost				
15G2AFD	gost		Japan		2
15G2AFDps	gost		SCr415	jis	
15HM	gost		SCr415H	jis	
15KH	gost				
15KHGN2TA	gost		Europe		1
15N2M	gost		17Cr3 This grade's own name	din-en	
15H2M	gost				
15HM	gost		France		1
15XГHTA	gost		12C3	afnor	
CT.15HM	gost				
CT.15H2M	gost		Spain		1
			F-1516	une	
United States		11			
G46150 This grade's own name	uns		Czechia		1
G50150 This grade's own name	uns		14120	csn	
G51150 This grade's own name	uns				
G51170 This grade's own name	uns		Slovakia		1
G61180 This grade's own name	uns		14 120	stn	
H61180 This grade's own name	uns				
4615 This grade's own name	aisi-sae		Poland		1
5015 This grade's own name	aisi-sae		15H	pn	
5117 This grade's own name	aisi-sae				
6118 This grade's own name	aisi-sae		Serbia		1
6118H This grade's own name	aisi-sae		Č.4120	srps	

Note on use. The data is compiled to the best of our knowledge from publicly available standards and manufacturer documentation. It replaces neither material testing nor an inspection document to EN 10204. Please request a mill certificate to EN 10204 2.1, 3.1 or 3.2 together with your enquiry. The standard in its current valid edition always prevails.

Enquiry about 15G2AFDps

[Start an enquiry](#)

Quotation, availability, mill certificate or a technical question — directly on the material page.

DATASHEET ONLINE

View the material page

GRADE SEARCH

Search all grades

MATERIAL NO.

1.7016

ISSUED

Aug 20, 2026