

2X13H4Г9

also listed as 20KH13N4G9

Chemical composition, mechanical and physical property values, and 4 standard designations from 1 regions.

OTHER DESIGNATIONS	PROPERTY VALUES
4 in 1 regions	7 on file

Chemical composition


Mass fraction in %

What this alloy is



Iron — the balance, never listed by a standard — 72.7 % Cr — 13 % Mn — 9 % Ni — 4.2 % Traces & impurities · 1.1 %

Logarithmic scale, 0.01 % to 100 % — every value here compares directly, decade by decade.

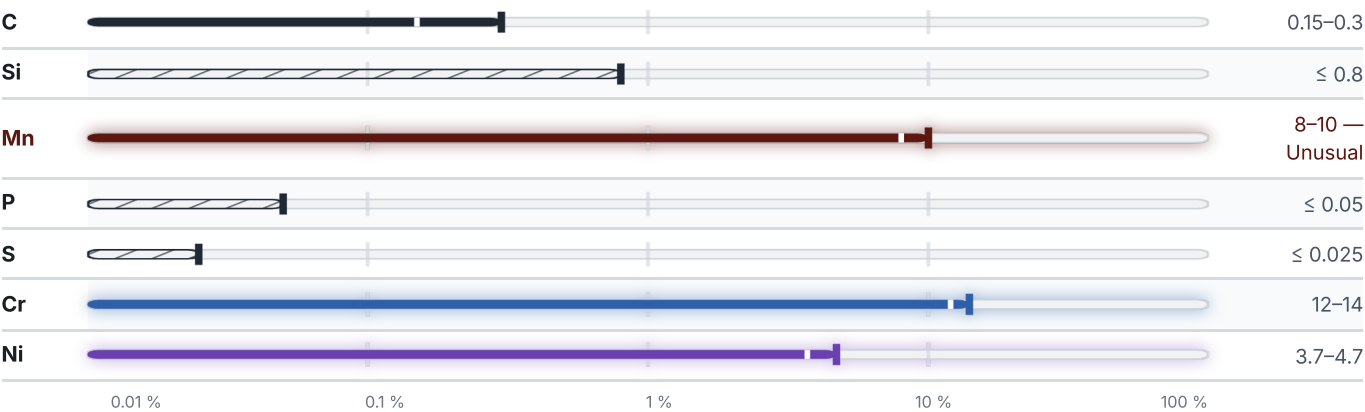

The scale is logarithmic, not the element's raw share of the alloy — the only honest way to fit 0.01 % and 100 % in one picture, and it means every value here can be compared with every other.

Predicted transformation temperatures

Not enough recorded composition to predict a transformation temperature for this grade — missing: Mo.

Mechanical properties

10 values across 4 conditions

CONDITION · DIMENSION	RM N/mm ²	RE N/mm ²	A5 %	Z %
Bar, GOST 5949-75	640	245	35	55

CONDITION · DIMENSION	RM N/mm ²	A5 %
Sheet thin, GOST 4986-79	590	18–35

CONDITION · DIMENSION	RM N/mm ²	A5 %
Sheet thin cold-worked , GOST 5582-75	980	15

CONDITION · DIMENSION	RM N/mm ²	A5 %
Sheet thin, GOST 5582-75	640	40

Designations across standards

4 designations · 1 documented as identical

Russia / CIS	4
20KH13N4G9 This grade's own name	gost
20X13H4Г9	gost
2X13H4Г9	gost
ЭИ100	gost

Note on use. The data is compiled to the best of our knowledge from publicly available standards and manufacturer documentation. It replaces neither material testing nor an inspection document to EN 10204. Please request a mill certificate to EN 10204 2.1, 3.1 or 3.2 together with your enquiry. The standard in its current valid edition always prevails.

Enquiry about 2X13H4Г9

Quotation, availability, mill certificate or a technical question — directly on the material page.

Start an enquiry

DATASHEET ONLINE

View the material page

GRADE SEARCH

Search all grades

MATERIAL NO.

—

ISSUED

Aug 15, 2026