

4X18H25C2

also listed as 36KH18N25S2


Chemical composition, mechanical and physical property values, and 3 standard designations from 1 regions.

OTHER DESIGNATIONS	PROPERTY VALUES
3 in 1 regions	8 on file


Chemical composition

Mass fraction in %

What this alloy is

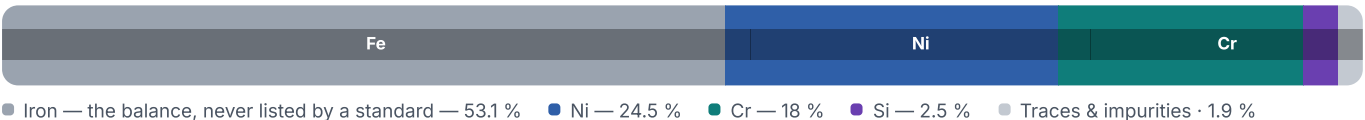

Logarithmic scale, 0.01 % to 100 % — every value here compares directly, decade by decade.

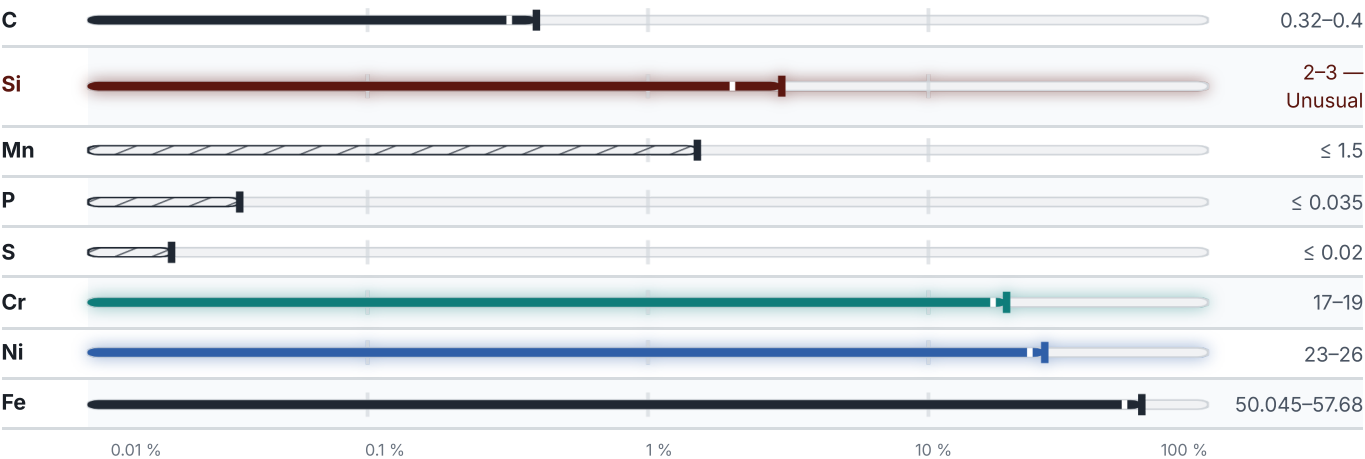

The scale is logarithmic, not the element's raw share of the alloy — the only honest way to fit 0.01 % and 100 % in one picture, and it means every value here can be compared with every other.

Predicted transformation temperatures

Not enough recorded composition to predict a transformation temperature for this grade — missing: Mo.

Mechanical properties

4 values across 1 conditions

CONDITION · DIMENSION	RM N/mm ²	RE N/mm ²	A5 %	Z %
Bar, GOST 5949-75	640	345	25	40

Physical properties

0 values

CONDITION · DIMENSION	RHO g/cm ³	E GPa	ALPHA 10 ⁻⁶ /K	LAMBDA W/(m·K)
20	7.8	200	—	—
100	—	—	13	15
200	—	191	13.4	—
300	—	186	14.7	—
400	—	178	—	—
500	—	171	16.1	22.8
600	—	162	—	25.5
700	—	154	—	26.3
800	—	147	—	37.4

Designations across standards

3 designations · 1 documented as identical

Russia / CIS	3
36KH18N25S2 This grade's own name	gost
36X18H25C2	gost
4X18H25C2	gost

Note on use. The data is compiled to the best of our knowledge from publicly available standards and manufacturer documentation. It replaces neither material testing nor an inspection document to EN 10204. Please request a mill certificate to EN 10204 2.1, 3.1 or 3.2 together with your enquiry. The standard in its current valid edition always prevails.

Enquiry about 4X18H25C2

Quotation, availability, mill certificate or a technical question — directly on the material page.

Start an enquiry

DATASHEET ONLINE	GRADE SEARCH	MATERIAL NO.	ISSUED
View the material page	Search all grades	—	Aug 15, 2026