

MATERIAL NUMBER 1.0044 · CLASS 1.0


1.0044

Chemical composition, mechanical and physical property values, and 130 standard designations from 25 regions.

DENSITY 7.85 g/cm³	OTHER DESIGNATIONS 130 in 25 regions	PROPERTY VALUES 7 on file
------------------------------	--	-------------------------------------

Chemical composition

Mass fraction in %

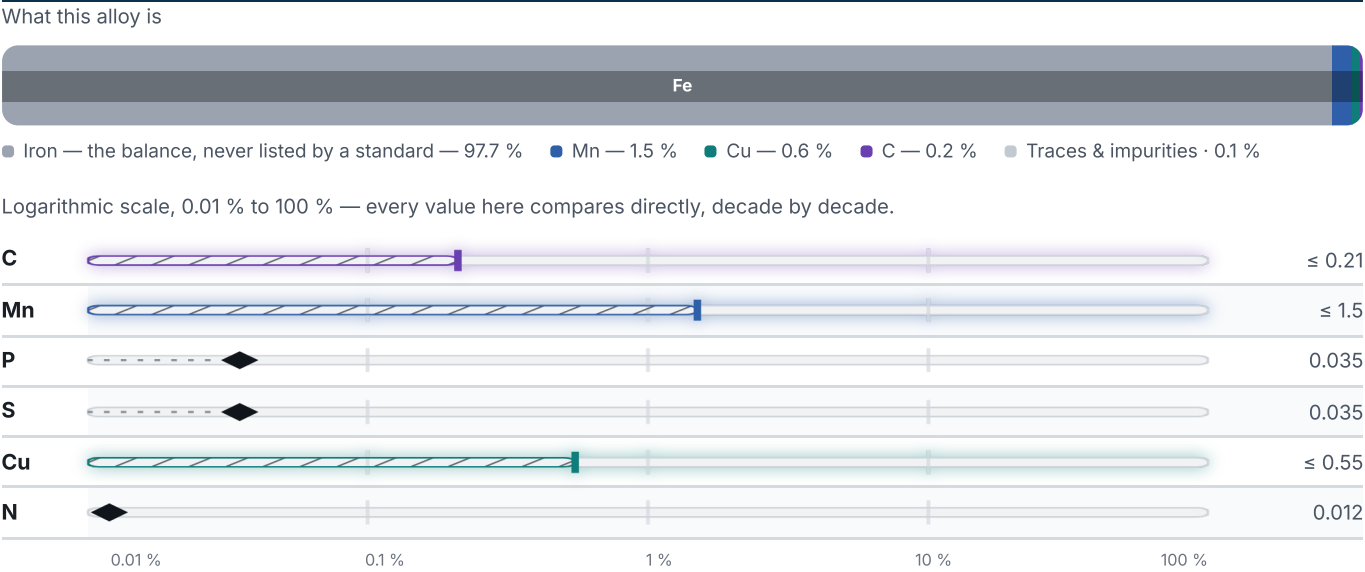

The scale is logarithmic, not the element’s raw share of the alloy — the only honest way to fit 0.01 % and 100 % in one picture, and it means every value here can be compared with every other.

Predicted transformation temperatures

Not enough recorded composition to predict a transformation temperature for this grade — missing: Si, Ni, Cr, Mo.

Mechanical properties

22 values across 2 conditions

FLAT AND LONG PRODUCTS	REH N/mm²	RM N/mm²
≤ 3	—	430–580
3 – 100	—	410–560

FLAT AND LONG PRODUCTS	REH N/mm ²	RM N/mm ²
≤ 16	275	–
16 – 40	265	–
40 – 63	255	–
63 – 80	245	–
80 – 100	235	–
100 – 150	225	400–540
150 – 250	–	380–540
150 – 200	215	–
200 – 250	205	–

CONDITION · DIMENSION	A80 % · Lo = 80 mm	A % · Lo = 5,65 √So
≤ 1	15	–
1 – 1.5	16	–
1.5 – 2	17	–
2 – 2.5	18	–
2.5 – 3	19	–
3 – 40	–	23
40 – 63	–	22
63 – 100	–	21
100 – 150	–	19
150 – 250	–	18

Physical properties1 values

CONDITION · DIMENSION	RHO g/cm ³	RHO_EL nΩ·m
20	7.65	500

PROPERTY	VALUE	UNIT
Density	7.85	g/cm ³

Designations across standards

130 designations · 13 documented as identical

United States	25	Japan	14
G10200	This grade's own name uns	SM400A	jis
K 02598	This grade's own name uns	SM400B	jis
K02301	This grade's own name uns	SM400C	jis
K02595	This grade's own name uns	SM41A	jis
K02596	This grade's own name uns	SM520B	jis
K02597	This grade's own name uns	SN400B	jis
K02598	This grade's own name uns	SN400C	jis
K02599	This grade's own name uns	SN490B	jis
K02702	This grade's own name uns	SN490C	jis
K03000	This grade's own name uns	SS400	jis
1020	This grade's own name aisi-sae	SS41	jis
A283D	aisi-sae	STK400	jis
A529	aisi-sae	STKM19C	jis
A570	aisi-sae	STKR400	jis
A570(40)	aisi-sae		
A570Gr.40	aisi-sae	Spain	7
A573Gr.70	aisi-sae	A430B	une
A611Gr.D	aisi-sae	AE255B	une
G10200	aisi-sae	AE275B	une
Gr.40	aisi-sae	AE275D	une
Gr.D	aisi-sae	Fe430BFN	une
GradeA	aisi-sae	Fe430D1FF	une
GradeD	aisi-sae	S275JR	une
K02702	aisi-sae		
A570	astm	International	6
		E275-C	iso
United Kingdom	20	E275-D	iso
1449-43/25HR	bs	E275B	iso
161-430	bs	Fe430-B	iso
4360-43B	bs	Fe430-C	iso
4360-43C	bs	Fe430-D	iso
43A	bs		
43B	bs	Europe	5
43C	bs	Fe430B	din-en
43D	bs	Gr.D	din-en
CEW4	bs	RSt42-2	din-en
ERW4	bs	S275JR This grade's own name	din-en
Fe430BFN	bs	St 44-2 This grade's own name	din-en
Fe430D1FF	bs		
Gr 43B	bs	China	5
HFS4	bs	Q225	gb
HFW4	bs	Q225A	gb
HS	bs	Q255	gb
S275J2G3	bs	Q255A	gb
S275JR	bs	Q275Z	gb
S275N	bs		
SAW4	bs		

Italy	5	Czechia	3
FE430B	uni	11423	csn
Fe430BFN	uni	11425	csn
Fe430C(FN)	uni	11443	csn
Fe430D(FF)	uni		
S275JR	uni	Belgium	3
Hungary	5	AE295B	nbn
45 B	msz	FE430BFN	nbn
A 44	msz	FE430D1FF	nbn
Fe275B	msz	Canada	3
FK	msz	260W	csa
S275JR	msz	260WT	csa
Bulgaria	5	38W	csa
BSt4ps	bds	Romania	2
BSt4sp	bds	OL42.1	stas
S275JR	bds	OL44.2	stas
WSt4ps	bds	Austria	2
WSt4sp	bds	St42F	onorm
France	4	St430B	onorm
E28-2	afnor	Norway	1
E28-3	afnor	NS12142	ns
E28-4	afnor	Portugal	1
S275JR	afnor	FE430-B	np
Poland	4	Slovakia	1
St4S	pn	11 443	stn
St4SY	pn	South Africa	1
St4V	pn	300 WB	sans
St4VY	pn	Finland	1
Russia / CIS	3	Fe44B	sfs
St4ps	gost	South Korea	1
St4sp	gost	STKM19C	ks
Cт4nc	gost		
Sweden	3		
1411	ss		
1412	ss		
1414	ss		

Note on use. The data is compiled to the best of our knowledge from publicly available standards and manufacturer documentation. It replaces neither material testing nor an inspection document to EN 10204. Please request a mill certificate to EN 10204 2.1, 3.1 or 3.2 together with your enquiry. The standard in its current valid edition always prevails.

Enquiry about 1.0044

Quotation, availability, mill certificate or a technical question — directly on the material page.

[Start an enquiry](#)

DATASHEET ONLINE

[View the material page](#)

GRADE SEARCH

[Search all grades](#)

MATERIAL NO.

1.0044

ISSUED

Aug 20, 2026