

MATERIAL NUMBER 1.0576 · CLASS 1.0


1.0576

Chemical composition, mechanical and physical property values, and 6 standard designations from 4 regions.

DENSITY 7.85 g/cm ³	OTHER DESIGNATIONS 6 in 4 regions	PROPERTY VALUES 6 on file
--	---	-------------------------------------

Chemical composition

Mass fraction in %

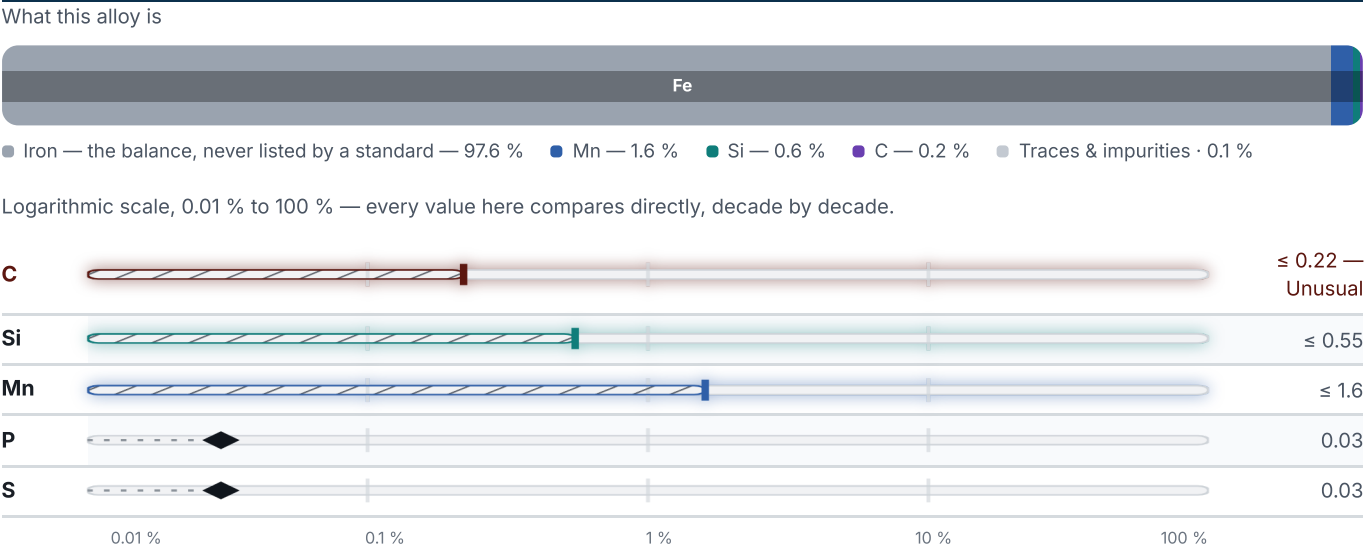

The scale is logarithmic, not the element's raw share of the alloy — the only honest way to fit 0.01 % and 100 % in one picture, and it means every value here can be compared with every other.

Predicted transformation temperatures

Not enough recorded composition to predict a transformation temperature for this grade — missing: Ni, Cr, Mo.

Mechanical properties

13 values across 1 conditions

CONDITION · DIMENSION	REH N/mm ²	RM N/mm ²	A %
≤ 3	—	510–680	—
3 – 100	—	470–630	—

CONDITION · DIMENSION	REH N/mm ²	RM N/mm ²	A %
≤ 16	355	–	–
16 – 40	345	–	–
40 – 63	335	–	21
≤ 40	–	–	22
63 – 80	325	–	–
63 – 100	–	–	20
80 – 100	315	–	–
100 – 120	295	450–600	18

Physical properties

1 values

PROPERTY	VALUE	UNIT
Density	7.85	g/cm ³

Designations across standards

6 designations · 4 documented as identical

Europe	3	Czechia	1
RoSt 52-3 This grade's own name	din-en	11503	csn
S355J2H This grade's own name	din-en		
St 52-3 N This grade's own name	din-en	Slovakia	1
		11 503	stn
United States	1		
K12709 This grade's own name	uns		

Note on use. The data is compiled to the best of our knowledge from publicly available standards and manufacturer documentation. It replaces neither material testing nor an inspection document to EN 10204. Please request a mill certificate to EN 10204 2.1, 3.1 or 3.2 together with your enquiry. The standard in its current valid edition always prevails.

Enquiry about 1.0576

Quotation, availability, mill certificate or a technical question — directly on the material page.

[Start an enquiry](#)

DATASHEET ONLINE	GRADE SEARCH	MATERIAL NO.	ISSUED
View the material page	Search all grades	1.0576	Aug 20, 2026