

MATERIAL NUMBER 1.4573 · CLASS 1.4

1.4573

Chemical composition, mechanical and physical property values, and 31 standard designations from 12 regions.

DENSITY 7.95 g/cm ³	OTHER DESIGNATIONS 31 in 12 regions	PROPERTY VALUES 12 on file
--	---	--------------------------------------

Chemical composition


Mass fraction in %

What this alloy is



● Iron — the balance, never listed by a standard — 61.5 % ● Cr — 23.5 % ● Ni — 5.5 % ● Mo — 5.3 % ● Traces & impurities · 4.3 %

Logarithmic scale, 0.01 % to 100 % — every value here compares directly, decade by decade.

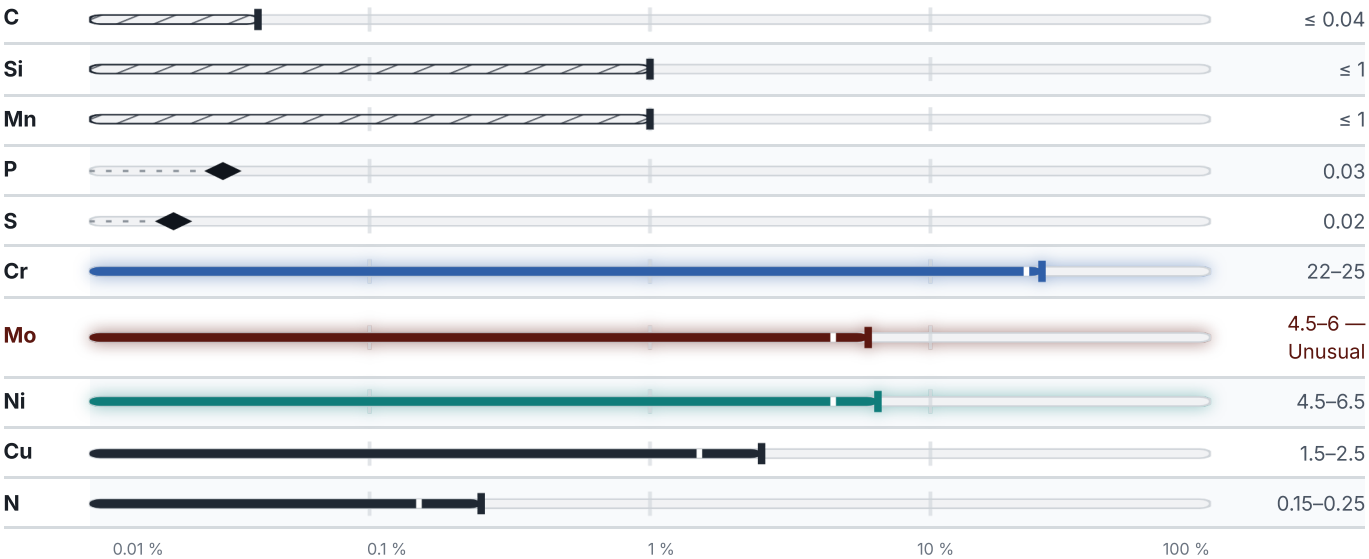

The scale is logarithmic, not the element's raw share of the alloy — the only honest way to fit 0.01 % and 100 % in one picture, and it means every value here can be compared with every other.

Predicted transformation temperatures

This grade's composition falls outside the published model's validated range (a low-alloy composition window), so no transformation temperature is predicted here.

Mechanical properties

18 values across 5 conditions

CONDITION · DIMENSION	RM N/mm ²	RE N/mm ²	A5 %	Z %	HB
Wire, GOST 18143-72	540–830	–	20–25	–	–
Forging, GOST 25054-81	510	196	30–38	40–50	–
10KH17N13M3T (10X17H13M3T) , Forging GOST 25054-81	–	–	–	–	200
CONDITION · DIMENSION	RM N/mm ²	RE N/mm ²	A5 %	Z %	
Bar, GOST 5949-75	530	196	40		55
CONDITION · DIMENSION	RM N/mm ²	RE N/mm ²	A5 %		
Sheet trick, GOST 7350-77	530	235			37
CONDITION · DIMENSION	RM N/mm ²	A5 %			
Sheet thin, GOST 5582-75	530				38
CONDITION · DIMENSION	RM N/mm ²	A5 %			
Sheet thin, GOST 4986-79	530				20–40

Physical properties

2 values

CONDITION · DIMENSION			RHO g/cm³
20			8
PROPERTY	VALUE	UNIT	
Density	7.95	g/cm³	

Technological properties

PROPERTY	VALUE	UNIT
Weldability	without limitations.	

Designations across standards

31 designations · 1 documented as identical

Russia / CIS		10	China		3
08KH17N13M2T	gost		0Cr18Ni12Mo3Ti		gb
08X17H13M2T	gost		1Cr18Ni12Mo2Ti		gb
0X17H13M2T	gost		1Cr18Ni12Mo3Ti		gb
10Ch17N13M2T	gost		Spain		2
10Ch17N13M3T	gost				
10KH17N13M3T	gost		F.3535		une
10X17H13M2T	gost		X6CrNiMoTi17-12-2		une
10X17H13M3T	gost		Czechia		2
X17H13M3T	gost				
ЭИ432	gost		17353		csn
United States		3	17356		csn
			Europe		1
			GX3CrNiMoCuN24-6-5	This grade's own name	din-en
S31635	uns		France		1
316Ti	aisi-sae				
S31635	aisi-sae		Z6 CNDT 17.12		afnor
United Kingdom		3	Italy		1
			X6CrNiMoTi17-13		uni
Japan		3	Sweden		1
			2350		ss
			Poland		1
SUS 316Ti	jis				
SUS 316TiTB	jis		H17N13M2T		pn
SUS 316TiTP	jis				

Note on use. The data is compiled to the best of our knowledge from publicly available standards and manufacturer documentation. It replaces neither material testing nor an inspection document to EN 10204. Please request a mill certificate to EN 10204 2.1, 3.1 or 3.2 together with your enquiry. The standard in its current valid edition always prevails.

Enquiry about 1.4573

Start an enquiry

Quotation, availability, mill certificate or a technical question — directly on the material page.

DATASHEET ONLINE

View the material page

GRADE SEARCH

Search all grades

MATERIAL NO.

1.4573

ISSUED

Aug 20, 2026