

MATERIAL NUMBER 1.6657 · CLASS 1.6


1.6657

Chemical composition, mechanical and physical property values, and 40 standard designations from 14 regions.


DENSITY 7.85 g/cm³	OTHER DESIGNATIONS 40 in 14 regions	PROPERTY VALUES 16 on file
------------------------------	---	--------------------------------------

Chemical composition

Mass fraction in %

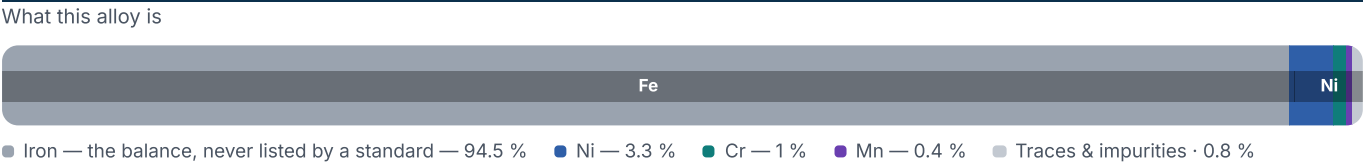

Logarithmic scale, 0.01 % to 100 % — every value here compares directly, decade by decade.

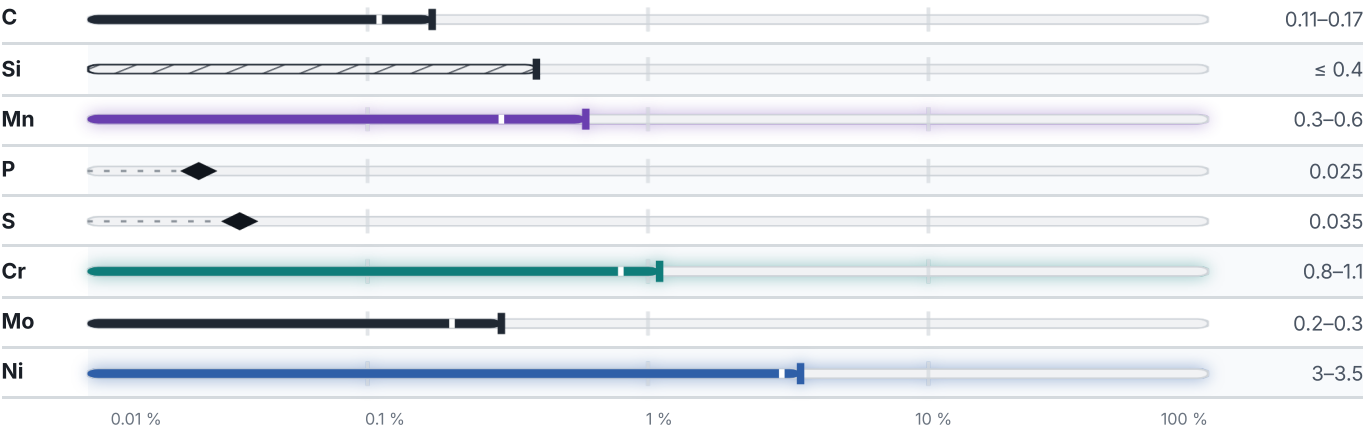

The scale is logarithmic, not the element's raw share of the alloy — the only honest way to fit 0.01 % and 100 % in one picture, and it means every value here can be compared with every other.

Predicted transformation temperatures

This grade's composition falls outside the published model's validated range (a low-alloy composition window), so no transformation temperature is predicted here.

Mechanical properties

11 values across 7 conditions

TREATED TO IMPROVE SHEARABILITY					HB
Treated to improve shearability					255
SOFT ANNEALED					HB
Soft annealed					241
TREATED TO HARDNESS RANGE					HB
Treated to hardness range					187–241
TREATED TO FERRITE-PEARLITE STRUCTURE AND HARDNESS RANGE					HB
Treated to ferrite-pearlite structure and hardness range					166–217
QUENCHING AND DRAWING	RM N/mm ²	RE N/mm ²	A5 %	Z %	KCU kJ/m ²
Ø 15	1130	835	12	50	980
CONDITION · DIMENSION					HB
(annealing) , GOST 4543-71					269
CONDITION · DIMENSION					RM N/mm ²
200					1200

Physical properties

8 values

CONDITION · DIMENSION	RHO g/cm ³	E GPa	ALPHA 10 ⁻⁶ /K	LAMBDA W/(m·K)
20	7.95	200	–	–
100	7.93	165	11.7	36
200	7.9	141	12.2	36
300	7.86	–	12.7	35
400	7.83	139	13.1	35
500	7.8	–	13.5	34
600	7.76	–	13.9	33
700	–	–	–	32
800	–	–	–	30

PROPERTY	VALUE	UNIT
Density	7.85	g/cm³
Transformation point Ac1	700	°C
Transformation point Ac3	810	°C
Transformation point Ar3	400	°C
Transformation point Ar1	350	°C

Technological properties

PROPERTY	VALUE	UNIT
Weldability	hard weldability.	
Flake sensitivity	predisposed	
Temper brittleness	not predisposed	

Heat treatment

1 regimes

STEP	TEMPERATURE	MEDIUM
Soft annealing	Temperature not stated	—

Designations across standards

40 designations · 7 documented as identical

United States		10	Russia / CIS		5
G93106		uns	14ChN3M		gost
H93100	This grade's own name	uns	14HN3M		gost
H93106	This grade's own name	uns	14KhN3M		gost
9310		aisi-sae	18KH2N4MA		gost
9310H	This grade's own name	aisi-sae	18X2H4MA		gost
9310RH	This grade's own name	aisi-sae			
E9310		aisi-sae	Spain		4
E9310H	This grade's own name	aisi-sae	131		une
EX1	This grade's own name	aisi-sae	14NiCrMo131		une
A322		astm	F.1569		une
			F.1569-14NiCrMo		une
United Kingdom		6	United States / Aerospace		3
36C		bs	6260		ams
832H13		bs	6265		ams
832M13		bs	6267		ams
835M15		bs			
EN36C		bs	Europe		2
S157		bs	1.6657		din-en
			14NiCrMo13-4	This grade's own name	din-en

France	2	Poland	1
16NCD13	afnor	18H2N4WA	pn
16NiCrMo13	afnor		
Italy	2	Hungary	1
15NiCrMo13	uni	~BNCMo 2	msz
16NiCrMo12	uni	Bulgaria	1
Japan	1	18Ch2N4MA	bds
SNCM815	jis	Austria	1
Czechia	1	BOHLERM130	onorm
16720	csn		

Note on use. The data is compiled to the best of our knowledge from publicly available standards and manufacturer documentation. It replaces neither material testing nor an inspection document to EN 10204. Please request a mill certificate to EN 10204 2.1, 3.1 or 3.2 together with your enquiry. The standard in its current valid edition always prevails.

Enquiry about 1.6657

Quotation, availability, mill certificate or a technical question — directly on the material page.

[Start an enquiry](#)

DATASHEET ONLINE	GRADE SEARCH	MATERIAL NO.	ISSUED
View the material page	Search all grades	1.6657	Aug 20, 2026