

MATERIAL NUMBER 1.4031 · CLASS 1.4

# F.3404

## Material no. 1.4031

also listed as X38Cr13

Chemical composition, mechanical and physical property values, and 56 standard designations from 17 regions.

| DENSITY                      | OTHER DESIGNATIONS      | PROPERTY VALUES   |
|------------------------------|-------------------------|-------------------|
| <b>7.7</b> g/cm <sup>3</sup> | <b>56</b> in 17 regions | <b>10</b> on file |

### Chemical composition


Mass fraction in %

What this alloy is



● Iron — the balance, never listed by a standard — 84.1 % ● Cr — 13.5 % ● Si — 1 % ● Mn — 1 % ● Traces & impurities · 0.4 %

Logarithmic scale, 0.01 % to 100 % — every value here compares directly, decade by decade.

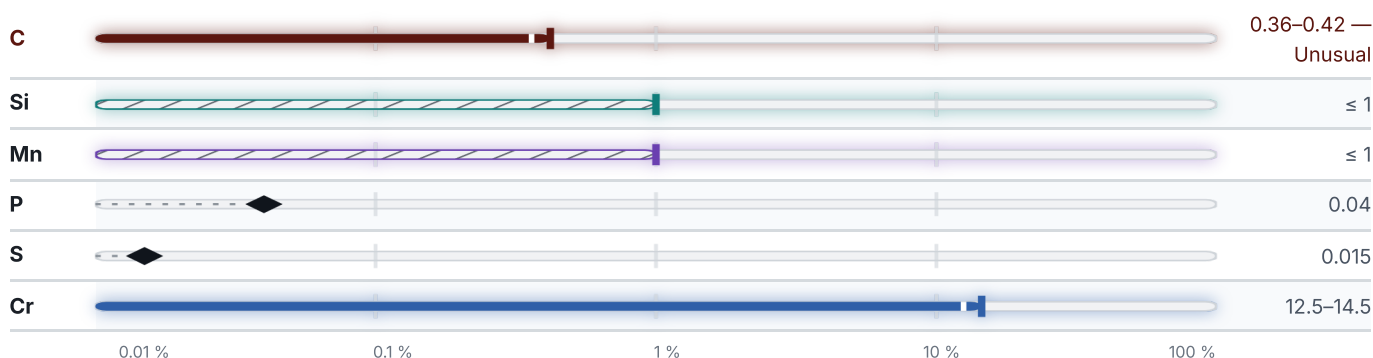

The scale is logarithmic, not the element's raw share of the alloy — the only honest way to fit 0.01 % and 100 % in one picture, and it means every value here can be compared with every other.

### Predicted transformation temperatures

Not enough recorded composition to predict a transformation temperature for this grade — missing: Ni, Mo.

## Mechanical properties

10 values across 4 conditions

| CONDITION · DIMENSION                              | RM<br>N/mm <sup>2</sup> | A5<br>% | HB      |
|----------------------------------------------------|-------------------------|---------|---------|
| Bar, GOST 18907-73                                 | 590–810                 | 10      | –       |
| Wire, GOST 18143-72                                | 640–880                 | 10–14   | –       |
| 40KH13 ( 40X13 ) (quenching, tempering)            | –                       | –       | 460–550 |
| 40KH13 ( 40X13 ) (annealing) , Bar<br>GOST 5949-75 | –                       | –       | 143–229 |
| SOFT ANNEALED                                      |                         |         | HV      |
| Soft annealed                                      |                         |         | 200–250 |
| QUENCHED AND TEMPERED                              |                         |         | HV      |
| Quenched and tempered                              |                         |         | 520–560 |
| CONDITION · DIMENSION                              | RM<br>N/mm <sup>2</sup> | A5<br>% |         |
| Sheet, GOST 5582-75                                | 550                     | 15      |         |

## Physical properties

4 values

| CONDITION · DIMENSION    | RHO<br>g/cm <sup>3</sup> | E<br>GPa | ALPHA<br>10 <sup>^-6</sup> /K | LAMBDA<br>W/(m·K) | CP<br>J/(kg·K) | RHO_EL<br>nΩ·m |
|--------------------------|--------------------------|----------|-------------------------------|-------------------|----------------|----------------|
| 20                       | 7.65                     | 218      | –                             | 25                | 461            | 590            |
| 100                      | 7.63                     | 214      | 10.8                          | 26                | 482            | 650            |
| 200                      | 7.6                      | 206      | 11.9                          | 27.2              | 523            | 710            |
| 300                      | 7.57                     | 198      | 12.3                          | 28.3              | 565            | 790            |
| 400                      | 7.54                     | 188      | 13                            | 29.1              | 607            | 860            |
| 500                      | 7.51                     | 176      | 13.6                          | 29.1              | 674            | 940            |
| 600                      | 7.48                     | 163      | 13.5                          | 29.1              | 775            | 1000           |
| 700                      | 7.45                     | 148      | 13.8                          | 28.3              | 988            | 1120           |
| 800                      | 7.42                     | 140      | 14.6                          | 27.9              | 825            | 1180           |
| 900                      | –                        | –        | –                             | 28.5              | 691            | 1160           |
| PROPERTY                 | VALUE                    |          | UNIT                          |                   |                |                |
| Density                  | 7.7                      |          | g/cm <sup>3</sup>             |                   |                |                |
| Transformation point Ac1 | 800                      |          | °C                            |                   |                |                |
| Transformation point Ar1 | 780                      |          | °C                            |                   |                |                |

## Technological properties

| PROPERTY    | VALUE        | UNIT |
|-------------|--------------|------|
| Weldability | is not used. |      |

## Designations across standards

56 designations · 3 documented as identical

|                      |          |                                  |        |
|----------------------|----------|----------------------------------|--------|
| <b>United States</b> | 16       | <b>Italy</b>                     | 3      |
| S42000               | uns      | X40Cr14                          | uni    |
| S42080               | uns      | X41Cr13KU                        | uni    |
| 420                  | aisi-sae | X46Cr13                          | uni    |
| 51420                | aisi-sae |                                  |        |
| S42000               | aisi-sae | <b>Sweden</b>                    | 3      |
| S42080               | aisi-sae | 2304                             | ss     |
| Type420              | aisi-sae | 2314                             | ss     |
| A1049                | astm     | SIS 2304                         | ss     |
| A176                 | astm     |                                  |        |
| A182                 | astm     | <b>Europe</b>                    | 2      |
| A276                 | astm     | X38Cr13                          | din-en |
| A314                 | astm     | X39Cr13                          | din-en |
| A473                 | astm     |                                  |        |
| A580                 | astm     | <b>United Kingdom</b>            | 2      |
| F1079                | astm     | 420S45                           | bs     |
| F2215                | astm     | X39Cr13                          | bs     |
|                      |          |                                  |        |
| <b>France</b>        | 8        | <b>United States / Aerospace</b> | 2      |
| X40Cr14              | afnor    | 5506                             | ams    |
| Z33C13               | afnor    | 5621                             | ams    |
| Z38C13M              | afnor    |                                  |        |
| Z40C13               | afnor    | <b>Czechia</b>                   | 2      |
| Z40C14               | afnor    | 17024                            | csn    |
| Z40Cr14              | afnor    | 19435                            | csn    |
| Z44C14               | afnor    |                                  |        |
| Z50C14               | afnor    | <b>Poland</b>                    | 2      |
|                      |          | 4H13                             | pn     |
| <b>Spain</b>         | 5        | 4H14                             | pn     |
| F.3404               | une      |                                  |        |
| F.3404-X40Cr 13      | une      | <b>International</b>             | 1      |
| F.3405               | une      | X40Cr14                          | iso    |
| X40Cr13              | une      |                                  |        |
| X45Cr13              | une      | <b>Japan</b>                     | 1      |
|                      |          | SUS 420J2                        | jis    |
| <b>Russia / CIS</b>  | 5        |                                  |        |
| 40Ch13               | gost     | <b>China</b>                     | 1      |
| 40KH13               | gost     | 4C13                             | gb     |
| 40X13                | gost     |                                  |        |
| 4X13                 | gost     | <b>Slovakia</b>                  | 1      |
| cr.40X13             | gost     | 17 024                           | stn    |

|        |      |                   |     |
|--------|------|-------------------|-----|
| Brazil | 1    | former Yugoslavia | 1   |
| 420    | abnt | Č.41731           | jus |

**Note on use.** The data is compiled to the best of our knowledge from publicly available standards and manufacturer documentation. It replaces neither material testing nor an inspection document to EN 10204. Please request a mill certificate to EN 10204 2.1, 3.1 or 3.2 together with your enquiry. The standard in its current valid edition always prevails.

### Enquiry about F.3404

Quotation, availability, mill certificate or a technical question — directly on the material page.

[Start an enquiry](#)

|                                        |                                   |              |              |
|----------------------------------------|-----------------------------------|--------------|--------------|
| DATASHEET ONLINE                       | GRADE SEARCH                      | MATERIAL NO. | ISSUED       |
| <a href="#">View the material page</a> | <a href="#">Search all grades</a> | 1.4031       | Aug 20, 2026 |